

## Effect of zinc oxid on the bentonite ability for removing Methylene blue from solution

*Zahra A. K. AL-Asadi\**

Received 23, October, 2012

Accepted 27, January, 2013

### Abstract:

A batch adsorption system was applied to study the adsorption of methylene blue from aqueous solution by Iraqi bentonite and treated bentonite with different amount of zinc oxide (ZnO). The adsorption capacities of methylene blue onto bentonite were evaluated. The equilibrium between liquid and solid phase was described by Langmuir model better than the Freundlich model. Langmuir and Freundlich constants have been determined. The separation factor or equilibrium parameter,  $R_L$  which is used to predict if an adsorption system is favourable or unfavourable was calculated for all cases.

**Keyword:** Adsorption capacities; Adsorption isotherm; Iraqi Bentonite; Methylene Blue.

### Introduction:

The purification of waste water contaminated by hazardous pollutants of inorganic and organic nature is among the serious problems of conservation, especially when such toxic materials (eg. dyes) contaminating the environment even in an insignificant concentration are involved. The elimination of such pollutants from aqueous solution is an important problem not only from a technical but also from an economic point of view. In order to minimize the possible damage to people and the environment, several studies have been conducted around the world [1-4].

Methods for decolorization have therefore become important in recent years. In principle; decolorization is possible with one or more of the following methods: adsorption, precipitation, chemical degradation, photodegradation and biodegradation [5]. Adsorption techniques have proven successful in removing colored organic species, with activated carbon

being the most widely used adsorbent due to its high capacity for the adsorption of organic materials [6]. However, due to activated carbon high cost and the difficulty of regeneration, effective adsorbent such as bentonite clay derivatives is needed. Bentonite is important clay having a variety of uses because of its colloidal property when it is mixed with water, swelling in water and in some organo environment and having high plasticity [7]. The industrial application of bentonite dispersions is very wide spread. Bentonite with its higher ion exchange capacity and surface area is used as an industrial raw material in sorptive, catalytic. They are used in different branches of industry, such as in drilling fluids, dyes, pharmaceutical application, paper, cement and ceramics. Bentonite dispersions have the advantage over other clays in being sensitive to surfactants, polymers and electrolytes [8]. The aim of this work was to study the effect of amount of ZnO on the ability of bentonite to

\*Department of Chemistry, College of Science, University of Baghdad.

remove the methylene blue from solution .

### Materials and Methods:


The bentonite clay was supplied from the state company for geological survey and mining-Iraq; the bentonite had the particle size less than 75 $\mu$ m. The molecular formula of bentonite could be written as [9] :

$Mg_2Al_10Si_{24}Fe_2O_{60} (OH)_{12}[Na, K, Ca]$

Bentonite which treated with zinc oxid was prepared by mixing 10g of bentonite and different amounts of zinc oxid (99.99% Gold Label FW

81.37, Merck) (1, 0.5, 0.1 and 0.05) g then shaken with 50 ml of distilled water for 24 h at room temperature, and then separated the solution by filtration process and drying in oven at 70 °C for 48 h.

The dye used was a methylene blue, (crystals, no.M 157/ 15/ 220 from M&B chemical co., of molecular weight 355.90) which correspond to the methylene blue hydrochloride, with 2H<sub>2</sub>O and the chemical formula is (C<sub>16</sub>H<sub>18</sub>ClN<sub>3</sub>S. 2H<sub>2</sub>O), and the formula of the methylene blue can be written as:

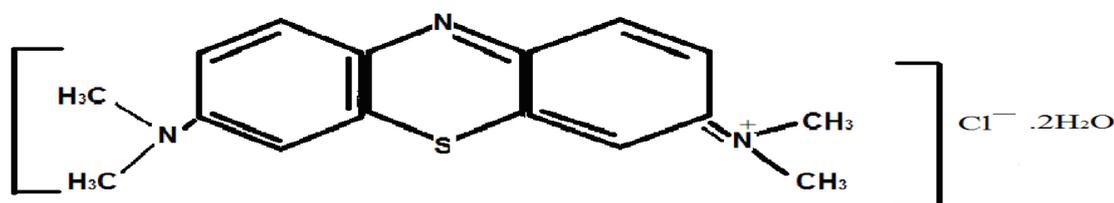

Stock solution of methylene blue was prepared and then diluted to give standard solutions of appropriate concentration. Batch experiments were conducted in 100 ml round flat bottom flasks and equilibrated using a magnetic stirrer. Then 10 ml aliquots of these standard solutions were placed in flasks and 0.1 g of bentonite powder was added, (the equilibrium contact time was 20 min.). After filtration, the solution of methylene blue in supernatant was analyzed at  $\lambda_{max}$  660

nm using uv-vis spectrophotometer (SP-3000 plus OPTIMA-Japan). The calibration curve was accomplished by measuring the absorbance of solutions at 660 nm. The plotting of absorbance vs. concentration was shown in Fig. 1. The amounts of adsorption were calculated by basing on the difference of methylene blue concentrations in aqueous solutions before and after adsorption. The adsorption capacity can be calculated as [10]:

$$\text{Adsorption capacity } (q_e) = \frac{(C_o - C_e) V}{W} \dots\dots (1)$$

Where  $C_0$  is the initial concentration (ppm),  $C_e$  is the final or equilibrium concentration (ppm);  $V$  is the volume

of the solution (ml) and  $W$  is the weight of the bentonite powder (g).

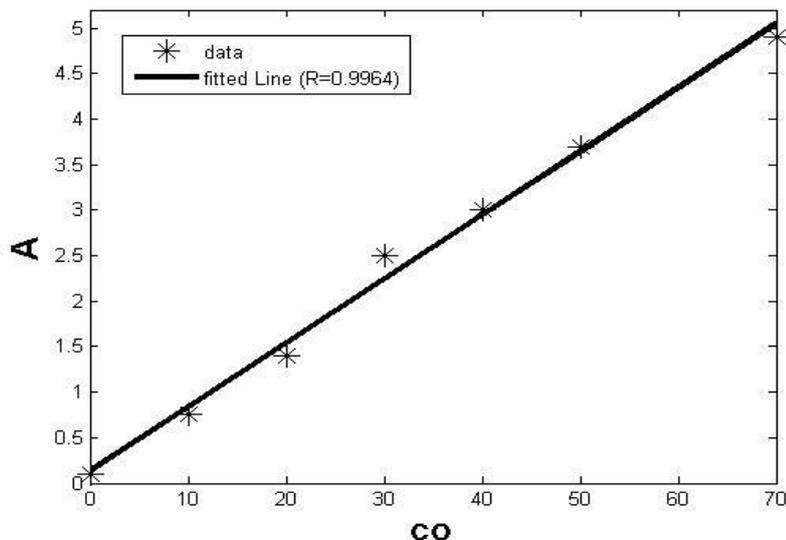


Fig.1- The calibration curve of various methylene blue concentration

**Results and Discussion:**

Fig. 2 shows the experimental equilibrium isotherms for adsorption of MB on bentonite surface, it show that when the amount of zinc oxide increases the  $C_e$  increases and  $q_e$  decreases. The results clearly show that the addition of competing

components systematically decreases the extent of adsorption.

The experimental values of the isotherm were used in the linear forms of Langmuir equation, which is valid for monolayer sorption . It is given by[11]:

$$C_e / q_e = C_e / Q + 1 / Qb \dots\dots\dots(2)$$

Where  $Q$  is the maximum adsorption at monolayer ( $mg\ g^{-1}$ ),  $C_e$  is the equilibrium concentration of methylene blue (ppm),  $q_e$  is the amount of methylene blue adsorbed per unit weight of bentonite powder at equilibrium concentration and  $b$  is the Langmuir constant or the adsorption

equilibrium constant ( $ml\ mg^{-1}$ ) and is a measure of the energy of adsorption. A linearized plot of  $C_e / q_e$  against  $C_e$  gives  $Q$  and  $b$  ( Fig. 3). The widely used empirical Freundlich equation basing on sorption on heterogeneous surface given by [11]:

$$\text{Log } q_e = \text{log}K_f + 1/ n \text{ log } C_e \dots\dots\dots(3)$$

Where  $K_f$  and  $n$  are Freundlich constants indicating sorption capacity and intensity, respectively.  $K_f$  and  $n$  can be determined from a linear plot of  $\text{log}q_e$  against  $\text{log}C_e$  Fig. 4.

The calculated results of the Langmuir and Freundlich isotherm constants and the correlation coefficients  $R^2$  are given in table 2.

Table 2 - Langmuir and Freundlich isotherm constants and correlation coefficients

adsorbent	Langmuir			Freundlich		
	Q(mg g <sup>-1</sup> )	b(ml mg <sup>-1</sup> )	R <sup>2</sup>	n	K <sub>f</sub> (mg g <sup>-1</sup> )	R <sup>2</sup>
Bentonite	357.14	0.451	0.998	-25.510	14.614	0.650
Bentonite + 1g ZnO	131.57	-0.002	0.968	-1.522	89.747	0.973
Bentonite + 0.5g ZnO	222.22	-0.004	0.982	-3.538	28.559	0.906
Bentonite + 0.1g ZnO	125	-0.002	0.943	-1.858	59.799	0.928
Bentonite + 0.05g	416.6	0.0043	0.953	-4.098	13.722	0.391

Basing on Fig. 3 the correlation coefficients R<sup>2</sup> reach to 0.998 in the case of Langmuir isotherm and R<sup>2</sup> was ranging between(0.391-0.973) for Freundlich which means the adsorption oby Langmuir rather than Freundlich. So MB make monolayer on the bentonite surface, and the value of maximum adsorption capacity Q was 357.14mg/g for bentonite and for bentonite with 0.05g of ZnO was 416.6 mg/g. The exponent n was less than

zero, an indication of an unfavourable Freundlich adsorption process.

It has been reported that the effect of isotherm shape with a view to predict if an adsorption system is favorable or unfavorable.[12] . The essential features of Langmuir isotherm can be expressed in term of a dimensionless constant separation factor or equilibrium parameter, R<sub>L</sub> which is expressed by the following equation: [13]

$$R_L = 1 / 1 + bC_o \dots\dots\dots (4)$$

Here C<sub>o</sub> is the initial concentration (ppm), and b is Langmuir constant

(ml/ mg). The parameters show the shape of isotherm according to table 3.

Table 3 - Effect of Separation Factor on Isotherm Shape[12]

R <sub>L</sub> value	Type of Isotherm
R <sub>L</sub> > 1	unfavorable
R <sub>L</sub> = 1	linear
0 < R <sub>L</sub> < 1	favorable
R <sub>L</sub> = 0	irreversible

Basing on the effect of separation factor on isotherm shape, the R<sub>L</sub> values are in the range of 0 < R<sub>L</sub> < 1, which indicates that the adsorption of MB on bentonite and modified bentonite

which treated with 0.05g ZnO are favourable.

The value of R<sub>L</sub> for different initial methylene blue concentrations are given in table 4..

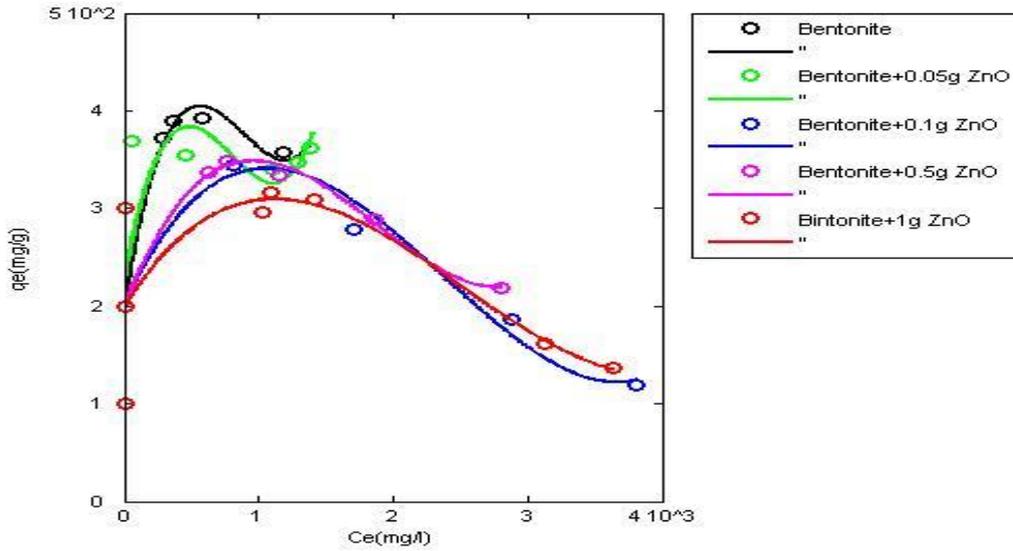


Fig.2 The adsorption isotherm of MB on Bentonite.

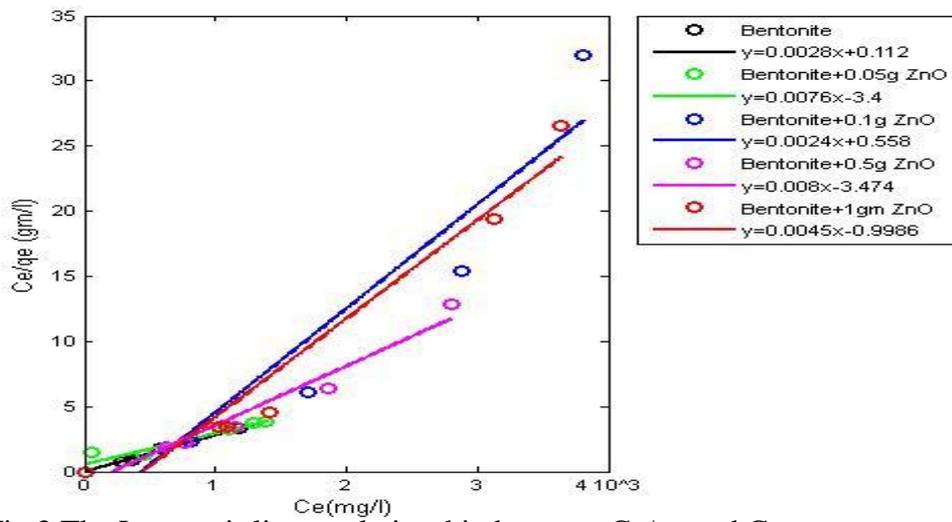


Fig.3 The Langmuir linear relationship between  $C_e/q_e$  and  $C_e$ .

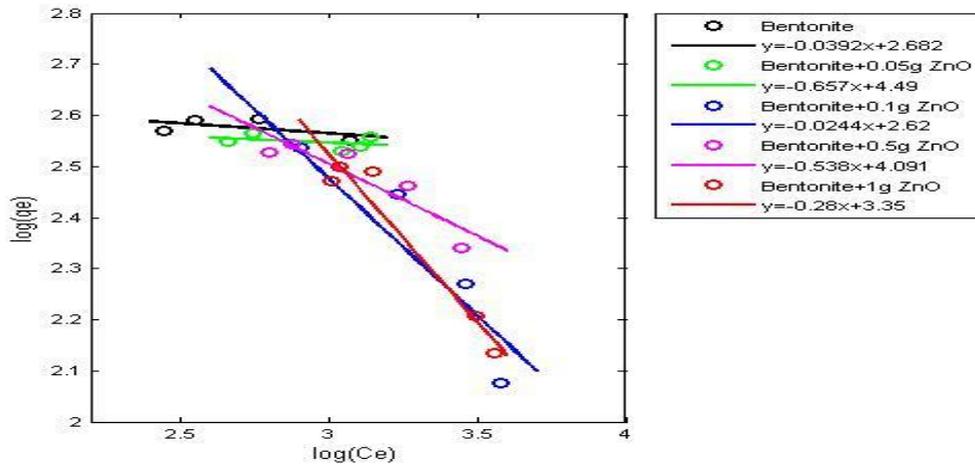


Fig.4 The Freundlich linear relationship between  $\log(q_e)$  and  $\log(C_e)$ .

Table 4 -  $R_L$  values based on the Langmuir equation

Initial conc. Of MB(ppm)*10 <sup>2</sup>	$R_L$ value				
	Bentonite	Bentonite+1g ZnO	Bentonite+ 0.5gZnO	Bentonite +0.1gZnO	Bentonite +0.05gZnO
10	0.038	-0.833	-0.285	-0.769	0.188
20	0.019	-0.294	-0.125	-0.277	0.104
30	0.013	-0.178	-0.080	-0.159	0.071
40	0.009	-0.128	-0.058	-0.121	0.054
50	0.007	-0.100	-0.046	-0.095	0.044

Bentonite and bentonite with 0.05 g ZnO can be considered to be microporous ; therefore pores are largely enough to let methylene blue ions through. The mechanism of ions adsorption on porous adsorbents may involve three steps; [14-15] (i) diffusion of the ions to the external surface of adsorbent; (ii) diffusion of ions into the pores of adsorbent; (iii) adsorption of the ions on the internal surface of adsorbent. The first step of adsorption may be affected by MB ions concentration and agitation period. The last step of the adsorption is considered as a rate-determining step and as a relatively rapid process.

### Conclusions:

In this study, the capacity of bentonite clay to adsorb Methylene blue ions from aqueous solutions was examined, including equilibrium studies. The adsorption isotherms could be well fitted by the Langmuir equation. The results show that degree of the interaction between the Methylene blue and the bentonite particles depends on the concentration of MB solution and the amount of zinc oxide used with bentonite. When the concentration of MB increases and the amount of zinc oxide increases the value of  $q_e$  decrease that means the dimerization of MB or desorption process take places for MB ions (Fig. 2). The value of maximum adsorption capacity  $Q$  for modified bentonite with 0.05g ZnO was more ability for removing methylene blue dye.

The results clearly show that the addition of competing components more than 0.05g ZnO systematically decreases the extent of adsorption.

### References:

1. Deorai R. and Guy R. D., 1981 Interactions of Some Large Organic Cations with Bentonite in Dilute Aqueous Systems. *clays and clay miner*, 29, (3), 205-212.
2. Gupta G.S., shackle MVB., Prasad G., and Singh V.N. 1992 China clay as an adsorbent for dye house wastewaters. *Environ. Tech.*, 13, 925-936.
3. Ceners J. and Schoonheydt, 1990 Proceeding of the 9<sup>th</sup> International Clay Conferenc, Strasbourg, 85, 15-23.
4. Margulies L., Rozen H. and Nir S., 1988 Model for competitive adsorption of organic cations on clays.. *Clays and Clay Miner* . 36, 270-276.
5. Zollinger H , 1991 color chemistry, VCH publishers Inc. NewYork.
6. Juang, R.S., Wu, F.C., and Tseng, R.L., 1997" the ability of activated clay for the adsorption of dyes from aqueous solutions", *Env. Tech.*, 18, 525-531.
7. Gunister, E; Isce, s; Alempar, A and Gungur, N. 2004 Effect of sodium Dodecyl sulphate on flow and electrokinetic properties of Na-activated Bentonite dispersions. *Bull. Matter. Sci.*, 27(3): 317-322.
8. Mockvciaikova, A and Orolinova, Z. 2009 Adsorption properties of Modified entonite clay. *ISSN*

- CHMINE TECHNOLOGUA. Nr. 1(50). 1231-1392.
9. Dawood ,G.S. 2006' Adsorption study of lead ions on the surface of ion exchange resin and some Iraqi clays' , M.Sc. thesis, uinv. Baghdad.
10. Ozlem C. and Demet B. 2001 Adsorption of some Textile Dyes by Hexadecyltrimethylammonium Bentonite. Turk J. chem. 25, 193-200.
11. Wan Ngah W.S. , Hanafiah M.A.K.M. and Yong S.S. 2008 Adsorption of humic acid from aqueous solutions on crosslinked chitosan-epichlorohydrin beads: Kinetics and isotherm studies. Colloids and Surfaces B: Biointerfaces 65, 18-24.
12. Weber, T. W and Chakravort, R. K. 1974 Pore and solid Diffusion Model for Fixed Bed Adsorbers. AICHEJ. 20. 228-238.
13. Hall, K. R; Eagleton, L. C; Acrivos, A. and Vermeulen, T. (1966) Pore and Solid Diffusion Kinetics in Fixed Bed Adsorption under Constant Pattern Condition. Ind. Eng. Chem. Fundam. , 5. 212-219.
14. Peniche-Covas, C. and Alvarez, L. W.; Arguelles-Monal, W. (1992) The Adsorption of Mercuric Ions by Chitosan. J. Appl. Polym. Sci. 46, 1147-1150.
15. Wan Ngah W.S. , Ab Ghani S. and Kamari A. (2005) Adsorption behaviour of Fe(II) and Fe(III) ions in aqueous solution on chitosan and cross-linked chitosan beads. Bio. Tech. 96, 443-450.

## تأثير اوكسيد الخارصين على قابلية البنتونايت في ازالة المثلين الازرق من المحلول

زهرة عبد الكريم عبد الرسول الاسدي\*

\*قسم الكيمياء، كلية العلوم، جامعة بغداد

### الخلاصة:

تم دراسة امتزاز صبغة المثلين الازرق على طين البنتونايت العراقي والبنتونايت المعامل مع كميات مختلفة من اوكسيد الخارصين. وقد تم تطبيق متساويات الحرارة للكميات وفرندلش ومن حساب الثوابت لهاتين المعادلتين تبين تطبيق موديل لانكماير افضل من موديل فرندلش كما تم حساب معامل الفصل او معامل التوازن ( $R_L$ ) لكل من البنتونايت والبنتونايت المعامل مع كميات مختلفة من اوكسيد الخارصين حيث من قيم ( $R_L$ ) تبين ان سطح البنتونايت المعامل مع 0.05 غم من اوكسيد الخارصين هو الافضل في قابلية امتزاز صبغة المثلين الازرق من محاليلها.