

**Effect of 1,4-Napthaquinone (NQ) and benzophenone (BPH) on the photodegradation and biodegradation of methyl cellulose film**

Salah M. Aliwi\*      Tariq S. Najim\*\*      Zainab Naeif Majeed\*\*\*

Date of acceptance 1/3 / 2010

**Abstract:**

The induced photodegradation of methyl cellulose (MC) films in air was investigated in the absence and presence of aromatic carbonyl compounds(photosensitizers): 1,4-naphthaquinone (NQ) and benzophenone (BPH) by accelerated weathering tester. The addition of (0.01 wt %) of low molecular weight aromatic carbonyl compounds to cellulose derivatives films(25µm in thickness) enhanced the photodegradation of the polymer films. The photodegradation rate was measured by the increase in carbonyl absorbance.

Decreases in solution viscosity and reduction of molecular weight were also observed in the irradiated samples. Changes in the number-average chain scission, the degree of deterioration and in the quantum yield of chain scission values are also observed, and it was concluded that branching or cross-linking has occurred for cellulose derivative with NQ and BPH. Findings from all analytical techniques indicated that the 1,4-naphthaquinone (NQ) photosensitizer enhance the photodegradation of methyl cellulose more than benzophenone (BPH).

The effect of the photosensitizer concentration, (ranging from 0.01 to 0.1 %), on the rate of photodegradation was also monitored for MC films. The rates are increased with increasing the photosensitizer concentration.

The effect of film thickness is also studied at fixed sensitizer concentration (0.05%), and results show that the rate of cellulose derivative photodegradation decreases with increasing film thickness.

The rate constants of the photodegradation of the photosensitizers deduced in cellulose derivatives films, [at concentration of (0.1%)by weight and thickness (25µm)].

Biodegradation of irradiated cellulose derivatives films was conclusively established with bacteria type *Pseudomonas aeuroginosa Rb-19* isolated from crude oil. The amount of bacteria growth on MC after 30 days was lower, while there was no growth observed in MC with BPH

**Key words: 1,4-Napthaquinone, benzophenone, biodegradation**

**Introduction**

Structural diversity and functional versatility of polysaccharides such as methylcellulose polymer and others are described in Dimitriu book<sup>(1)</sup>, while photodegradation details for these polymers are given in the literature<sup>(2-6)</sup>.

Cellulose ethers such as methylcellulose undergo photo-rheological change when exposed to ultraviolet (UV) radiation<sup>(2-6)</sup>. A major cause of such change is the main chain scission as a result, the molar mass

\* Ministry of Higher Education & Scientific Research

\*\*Mustansiriya University, College of Science, Department of Chemistry

\*\*\*Mustansiriya University, College of Science, polymer research unit

and, therefore, the molecular dimensions of the polymer conformational state, also, change.

During UV-irradiation of polymers the concentration of functional groups on the chain ends and inside macromolecules (double bonds and carbonyl groups) increases. It probably makes polymers more susceptible to attack of bacteria in natural environment<sup>(7)</sup>. biodegradable polymers have currently attracted high interest as ideal carriers in drug delivery and tissue engineering applications. In situ forming devices based on these materials will synergistically provide the advantages of the customary prefabricated devices as well as ease of administration<sup>(8)</sup>. In the present work, we describe the effects of Naphthaquinone (NQ), benzophenone (BPH) as photosensitizers on the degradation of methyl cellulose and study of its biodegradation.

## Martial and Methods:

### a- Film Preparations

1% of (MC)polymer solutions in acetone is used to prepare (25µm)polymer films which is measured by a micrometer type,(2610 a Germany)with and without various concentrations of (BPH, NQ) photosensitizers, The films were prepared by casting and evaporation techniques at room temperature for 12 hr., To remove the possible solvent residue, the film samples were further dried at room temperature for three hours under reduced pressure. The films were fixed on a special holder for irradiation (which is made from aluminum plate (0.6 mm) in thickness supplied from (Q-panel) company).

### b- Irradiation Experiments

The accelerated weather-o- meter, Q.U.V. tester,(Q-panel company, U.S.A),was used for irradiation of polymer films. The accelerated weathering tester contains stainless steel

plate with two cavities in the front and rear sides. Each side contains four lamps, type (U.V.B.313) located horizontally, giving spectrum range of wavelength between 290 to 360 nm and the maximum intensity is located at the wavelength 313 nm .The polymer film holders are fixed vertically and parallel to the lamps ,so that the UV radiation is vertically incident on the polymeric samples .

The irradiated sample holders were changed in positions from time to time to ensure that all samples received the same intensity of light.

During the irradiation process, the degree of photodegradation of polymer films was monitored by taking different exposure times.

### c- Determination of Viscosity Average Molecular Weight $(\bar{M}_v)$ Using Viscometry method

The viscosity property was used to determinate the molecular weight of the polymers using Mark -Houwink relation<sup>[9]</sup>

$$[\eta] = K (\bar{M}_v)^\alpha \quad \dots(1)$$

where,

$[\eta]$  = intrinsic viscosity

K and  $\alpha$ : are constants for a given polymer at a given temperature in a given solvent.

The intrinsic viscosity of a polymer solution was measured with an Ostwald U-tube viscometer .Solutions were made by dissolving the polymer in a solvent (g/100mL) and the flow times of polymer solution (t)and pure solvent (t<sub>0</sub>),were measured respectively.

### d- Ultraviolet Visible Spectrophotometry (U.V)

The absorption spectra was recorded using the ultraviolet visible spectrophotometer type (Hitachi U-2000), in the wavelength range between 200 to 800 nm.

### e- Infrared Spectrophotometry (IR)

The (IR) spectra were recorded using Pye Unicam, SP3-100 spectrophotometer. In this work the band index method was used, by comparing IR absorption peaks at the specified position with reference peak e.g. measurements changed in hydroxyl peak in relation to the reference band at  $2950\text{ cm}^{-1}$ , which refers to the C-H aliphatic, and changed in carbonyl peak in relation to the reference band at  $1430\text{ cm}^{-1}$  which refers to the  $\text{CH}_2$  bending in cellulose derivatives.

### Results and discussion

The photodegradation of (MC), which has specifically been studied, is used as a thickening agent and emulsifier in cosmetics, pharmaceuticals and clarity in various industrial fields<sup>[1]</sup>.

The UV-visible spectrum of irradiated MC film ( $25\mu\text{m}$  in thickness) at different time intervals shows the decrease in absorbance in the region (200-300)nm which due to the scission of main chain bonds in MC polymer. The spectra changes during photolysis of MC films ( $25\mu\text{m}$  in thickness) with 0.1% of NQ and BPH photosensitizers are shows the decrease in absorption in the region at wavelength below 300 nm which attributed to photodissociation of the photosensitizers with macromolecular chain breaking.

The IR spectrum of MC film (control) ( $25\mu\text{m}$  in thickness) shown small changes in carbonyl group located at  $1730\text{ cm}^{-1}$  after 200 hr of irradiation time. The photoactivity of MC film (control) ( $25\mu\text{m}$  in thickness) and with 0.1% of BPH and NQ photosensitizers is followed by the growth of carbonyl group only which is expressed in term carbonyl index ( $I_{\text{CO}}$ ) where calculated and tabulated with irradiation time in table (1).

It has been observed that the carbonyl index increase greatly with

irradiation time for MC films with BPH and NQ photosensitizers compared to MC film (control).

Accordingly, these photosensitizers are considered as photoinducers for MC films degradation.

**Table (1) Calculated values of carbonyl index ( $I_{\text{CO}}$ ) with irradiation time for MC film ( $25\mu\text{m}$  in thickness) containing 0.1 wt% of photosensitizers.**

photosensitizer concentration	Irradiation time					
	0	22	72	144	200	360
MC(control)	0	0	0	0	0.093	0.1
MC+NQ	0	1.181	1.59	2.039	2.53	2.611
MC+Bph	0	0.253	0.5004	1.639	1.72	1.813

The photosensitizers can be degrade the MC polymer via the generation of free radical. The produced radicals from irradiated photosensitizers can abstract hydrogen from the methyl group of the MC polymer to resulting the photodissociation.

These results are agreement with PMMA-CO-CMA film photodegradation by BPH reported by Yoshikatsu and co-workers<sup>[10]</sup>.

Also these results show that NQ act as better inducer for MC photodegradation compared to BPH, as the rate of carbonyl index formation is higher than that for similarly exposed MC (control) or MC with BPH. The above result is similar to results of photodegradation of poly styrene<sup>[11]</sup> and cellulose<sup>[12]</sup>.

### Effect of Film Thickness

The rate of photodegradation of MC films was studied in different thickness (25, 75 and  $150\mu\text{m}$ ) with fixed concentration (0.05 %) of BPH photosensitizer.

The calculated values and relationships between carbonyl index and irradiation time are tabulated in table (2).

It can be observed from the results in the abovementioned table and figure that carbonyl index ( $I_{\text{CO}}$ ) decrease with

increasing film thickness, which is attributed to a longer residential time for the oxygen to diffuse within the thicker MC layers.

**Table(2) :Calculated values of carbonyl index ( $I_{CO}$ )with irradiation time for MC with different thickness containing 0.05wt% of BPH.**

Thickness $\mu\text{m}$	Irradiation time				
	0	22	72	144	200
25	0	1.181	1.363	1.437	1.513
75	0	0.411	0.64	.887	1.509
150	0	0.38	0.5	0.866	1.2125

#### Effect of Photosensitizer Concentration

In the present work, the photodegradation of MC films (25  $\mu\text{m}$  in thickness) was also examined with different photosensitizer concentration.

Tables (3) and (4) show the calculated values of carbonyl index ( $I_{CO}$ ) with different irradiation times using different concentration of BPH and NQ photosensitizers, ranging from 0.00 % (MC control) to 0.1 % (wt/wt %).

It can be observed from the below tables, that the carbonyl index increase with increasing photosensitizer concentration, the rates of carbonyl index ( $I_{CO}$ ) formation are higher than those of the similarly exposed MC (control), confirming that these photosensitizers are accelerators for MC degradation.

One might suggest that oxidative degradation of MC is greatly enhanced in the presence high concentration of photosensitizers as seen in cellulose acetate. The difference in reactivity of the photosensitizers is also noticed from the differences in the rates of carbonyl index formation. BPH shows the lowest reactivity in degradation of MC polymer compared to NQ.

**Table (3) :Calculated values of carbonyl index ( $I_{CO}$ ) with irradiation time for MC film (25 $\mu\text{m}$  in thickness) containing different concentration of NQ photosensitizer.**

sensitizer concentration	Irradiation time					
	0	22	72	144	200	360
MC(control)	0	0	0	0	0.093	0.1
0.01%	0	0.54	0.919	1.528	1.54	1.632
0.05%	0	0.205	1.38	1.508	1.587	1.668
0.1%	0	1.181	1.59	2.039	2.53	2.611

**Table (4) :Calculated values of carbonyl index ( $I_{CO}$ ) with irradiation time for MC (25 $\mu\text{m}$  in thickness) containing different concentration of BPH photosensitizer.**

sensitizer concentration	Irradiation time					
	0	22	72	144	200	360
MC(control)	0	0	0	0	0.093	0.1
0.01%	0	0.2935	0.6219	1.0486	1.1	1.156
0.05%	0	0.118	1.363	1.437	1.513	1.592
0.1%	0	0.253	0.5004	1.639	1.72	1.813

#### Molecular Weight Changes During Photolysis

In the present work, the application of Mark-Houwink-Sakurada<sup>[97]</sup> (equation 1) in degradation of MC films was examined. The degradation was followed by the determination of the change in molecular weight by measuring the intrinsic viscosity.

Viscosity measurements for MC films (control) (25  $\mu\text{m}$  in thickness) and with 0.1 wt% of BPH and NQ photosensitizers were carried out before and after irradiation time, in distilled water solvent at 25°C. The MC films with BPH and NQ photosensitizers are not dissolved in distilled water after 20 hr irradiation, therefore it is assumed that crosslinking or branching occurs during photolysis course.

The problem of photocrosslinking of polymers is very important effected on account of the wide applications in commercial processes. Photo polymers are macromolecules which can become crosslinked polymers by the formation of interchange bonds under the influence of light.

Tsuda<sup>[13]</sup> has suggested that the energy from an excited triplet state of the sensitizer can be transferred to the triplet state of the polymer group which then undergoes crosslinking reaction as in equation (10).





These results are in an agreement with a previous study<sup>[137,138]</sup> which indicated that benzophenone and its derivatives cause extensive crosslinking of polyethylene. The change in molecular weight  $M_v$  of MC film (control) with irradiation time is shown in table (5) .



The degree of deterioration ( $\alpha$ ) and the average number of chain scissions( $S$ ) are also calculated in table (5) where they are increased with irradiation time which indicating to random breaking of bonds in the MC polymer chain. The quantum yield of the chain scission ( $\Phi_{cs}$ ) calculated for MC film is equal to( $1.38 \times 10^{-3}$ ).

**Table(5) :The variation of  $\alpha$ ,  $S$ ,  $P_t$  ,  $dM_v/dt$  ,  $(M_v)^2$  and  $M_v$  with irradiation time for MC films (control) (25  $\mu$ m in thickness) .**





Time(hr)	$M_v$	$(M_v)^2_{16}$	$d$ $M_v/dt$	$P_t$	$1/P_t$	$\alpha$	$S$
0	111 74	1248	97	57.5 36	0.017 36		
22	820 3	672	135.0 45	42.2 85	0.023 6	0.006 3	0.36 22
144	740 9	548	26.14 6	38.1 91	0.026 2	0.008 8	0.50 8
192	729 6	532	20.19 8	37.6 08	0.026 6	0.009 23	0.53 16
288	700 0	490	14.49 3	36.0 82	0.027 7	0.010 35	0.59 64

Therefore the suggesting mechanism for photodegradation of MC by photosensitizers is that:

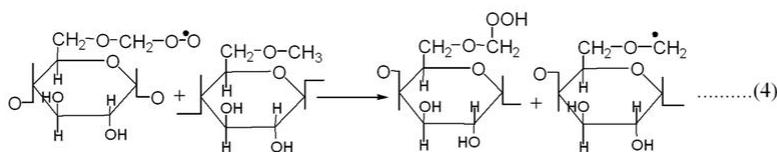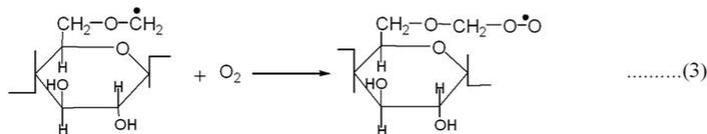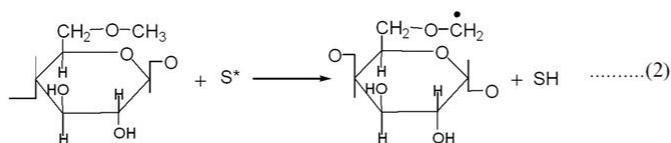

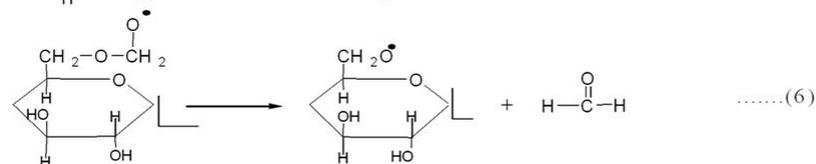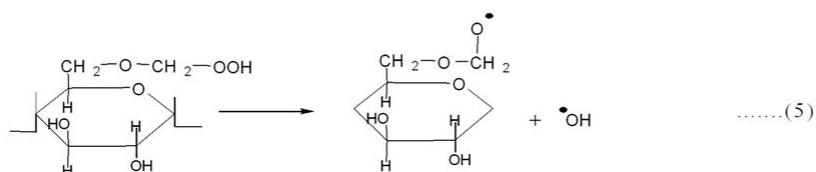

S = Photosensitizers (BPH, NQ)  
 SH= BPH-H or NQ-H

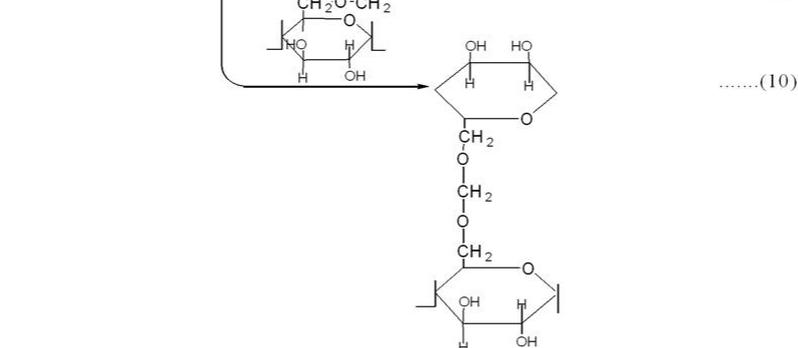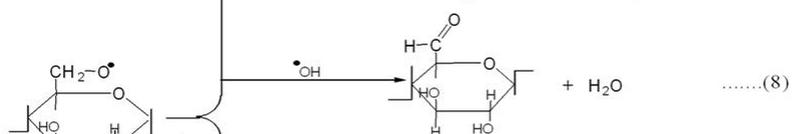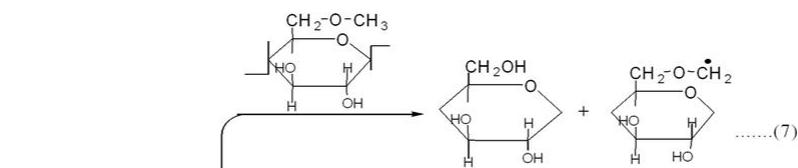

**Biodegradation of Cellulose Derivatives**

The bacteria, *Pseudomonas aeruginosa RB-19*, which is used in this work, was isolated from crude oil as utilizing of aliphatic and aromatic hydrocarbons(such as phenol and n-hexane).

In order to ensure that the bacteria isolated were indeed capable of growing with irradiation polymers as the sole available carbon source. Series of experiments was carried out in which the growth with polymer was compared to that in control [mineral medium( MM ) free of carbon source

J. The Growth of bacteria (*Pseudomonas aeruginosa RB-19*) on cellulose derivatives after photolysis is 10-20%

Our results support the conclusion that these bacteria were indeed capable of a significant amount of growth when the only carbon source present was the polymer. Color changes from colorless solution to green solution indicating microbial growth.

The biodegradation are followed by percentage weight loss of polymer through biodegradation, where the polymer precipitated by mixture of ethanol and water from bacteria solution and dried under vacuum.

**% loss weight = weight of polymer before biodegradation - weight of polymer after biodegradation**

The % loss weight for cellulose diacetate is 34%. In general, during UV-irradiation of polymers the concentration of functional groups on the chain ends and inside macromolecules (double bonds and carbonyl groups) increases. It probably makes polymers more susceptible to attack of bacteria in natural environment. It is also well known that the efficient main chain scission in irradiated polymers causes their mechanical deterioration and breaking on to small pieces. Thus, the access of oxygen and microorganisms is facilitated to the bulk of such destroyed products. In this way polymers become biodegradable.

The biodegradation of cellulose ethers has been studied and it is known that MC has low degraded because the microorganism attacks the unsubstituted residues of the polymers, the ether linkages to the cellulose backbone are considered resistant to microbial attack. The crosslink which occurred during photodegradation of MC with 0.1 wt% BPH prevent the biodegradation of MC along (30) days.

## Conclusion

It has been found that photooxidative degradation of methyl cellulose (MC) are more efficient in the presence of these photosensitizer, and 1,4-Naphtaquinone, Benzophenone are higher action, especially in sample contained (0.1wt%). The rates of degradation in cellulose derivatives films are inversely related to film thickness. Increasing film thickness can limit oxygen diffusion; therefore reduce the degradation rate of the polymer films.

Calculation based on the viscosity average molecular weight ( $M_v$ ) clearly indicates an overall decrease in molecular weight during irradiation. From the calculated values of the degree of deterioration ( $\alpha$ ) and the number average chain scission ( $S$ ), it is concluded that the type of degradation is random.

Methyl cellulose are biodegradable polymers and can be expected to be degraded in natural environmental systems. The rate of biodegradation cellulosic polymers to readily participate in nature's carbon cycle. This work, however, show that cellulose acetate has potentially degradable in the environment.

## References

1. S.Dimitriu, "Polysaccharides; structural diversity and functional versatility", New York, (2005).
2. G.Geuskens, "Photodegradation of polymers", Amsterdam, (1975).
3. J.F.Rabek, "Oxidative degradation of polymers", Amsterdam, (1975).
4. C.I.McNeill, "Fundamental aspects of polymer degradation", Cambridge, (1992).
5. R.A.Wach, H.Kudoh, Y.Muroya, Y.Kasumura and F.Yoshi, "Polysaccharides derivatives crosslinked by ionizing radiation", Budapest, (2005).

6. E. EL-Taboni, "On the viscose behavior of aqueous MC before and after photodegradation", M.Sc. Thesis, Benghazi, Garyounis University, (2006).
7. G.Scott , ICS- INDO Report. "Environmental Degradable Plastics". 20-24 March, (2000).
8. A.S.H.Doulabi, H.Mirzadeh, M.Imani, S.Shahriar, M.Atai and S.M.Ataei, "Synthesis and preparation of biodegradable and visible light crosslinkable unsaturated fumarate-based networks for biomedical applications", Polymers for advanced technologies, 19 (2008) 1199 .
9. W.Pigman and D.Horton,"The Carbohydrates Chemistry and Biochemistry", 2<sup>nd</sup>,Vol. IIA,pp.432-433,(1970)
10. ITO.Yoshikatsu,Y.Aoki,T. Matsuura, N.Kawatsuki and M. Uetsuki,*J. Appl. Polym. Sci.* ,42,409-415,(1991)
11. J.F.Rabek and B.Ranby, *J. Polym.Sci.,A1* .12,295,(1974)
12. C.Kujirai,K.Tsubakiyama,N.Hondo and K.Toda,*Kogyo Kagaku Zasshi*,73, 1701,(1970)
13. M.Tsuda, , *J. Polym.Sci.Phot. Japan*.32,51,(1969)

### تأثير 1،4- نفتاكوينون و بنزوكوينون والتكسر الضوئي والحيوي لفلم مثيل سليلوز

زينب نايف\*\*\*

صلاح محسن\*\*

طارق نجم\*

\*وزارة التعليم العالي والبحث العلمي.  
\*\* قسم الكيمياء- كلية العلوم – الجامعة المستنصرية.  
\*\*\*وحدة ابحاث البوليمر- كلية العلوم – الجامعة المستنصرية.

#### الخلاصة

تضمن هذا البحث دراسة التجزئة الضوئية المحتثة لافلام المثيل السليلوز في الهواء بوجود وعدم وجود بعض مركبات الكربونيل الاروماتية (متحسسات ضوئية ) التالية:

[1,4-Napthaquinone (NQ) and benzophenone (BPH)]

وقد تم التشعيع بواسطة جهاز التعجيل الحاوي على مصابيح فلورسنت لدراسة عملية التجزئة الضوئية هذه . ان اضافة (0.1wt%) من مركبات الكربونيل الاروماتية الى افلام مشتق السليلوز بسلك (25 مايكروميتر) يزيد التجزئة الضوئية للبوليمر . تم قياس التجزئة الضوئية بواسطة الزيادة في امتصاص الكربونيل. كما تم ملاحظة النقصان في اللزوجة والوزن الجزيئي من خلال متابعة التغير في المعدل العددي لقطع السلسلة ودرجة التجزئة وفي قيم منتج الكم لعملية قطع السلسلة. وقد وجدنا بان التفرع والتشابك العرضي يحصل في مشتق السليلوز مع (NQ, BPH). اظهرت نتائج التحليل ان 1,4-Napthaquinone (NQ) تزيد التجزئة الضوئية لمشتق السليلوز اسرع من benzophenone (BPH). كذلك تم دراسة تأثير تركيز المضافات في المدى (0.1-0.01%) على سرعة التجزئة الضوئية. وقد اظهرت النتائج ان سرعة التجزئة الضوئية تزداد بزيادة تركيز المضاف . و تم كذلك دراسة تأثير سمك الرقائق البوليمرية عند تركيز ثابت من المضاف (0.05%) وقد اظهرت النتائج ان التجزئة الضوئية تقل مع زيادة سمك الرقائق البوليمرية. إضافة الى ذلك تم اجراء تجارب على التجزئة الحيوية لمشتقات السليلوز المشععة باستخدام بكتريا *Pseudomonas aeuroginosa RB-19* معزولة من النفط حيث وجد ان نمو البكتيريا على المثيل سليلوز بعد 30 يوم يكون قليل , كما لم يلاحظ نمو أي بكتيري على المثيل سليلوز الحاوي على مضاف (BPH) .