

DOI: <http://dx.doi.org/10.21123/bsj.2022.19.4.0759>

## Recycling of Chicken Egg Shells into Nanopowder: Synthesis, and its Properties

Saffanah Khuder Mahmood<sup>1\*</sup>   
Shahbaa Khalil Ebrahim<sup>2</sup> 

Ghada Abdulrhman Sultan<sup>1</sup>   
Ammar Ghanim Mohammed Alhaaik<sup>1</sup> 

<sup>1</sup>Department of Anatomy, College of Veterinary Medicine, University of Mosul, Mosul, Iraq.

<sup>2</sup>Department of Pathology, College of Veterinary Medicine, University of Mosul, Mosul, Iraq.

\*Corresponding author: [saffanhjeber@uomosul.edu.iq](mailto:saffanhjeber@uomosul.edu.iq)

E-mail address: [Aliabc898@uomosul.edu.iq](mailto:Aliabc898@uomosul.edu.iq), [Shahbaa\\_khal@uomosul.edu.iq](mailto:Shahbaa_khal@uomosul.edu.iq), [Alhaaik\\_ag@uomosul.edu.iq](mailto:Alhaaik_ag@uomosul.edu.iq)

Received 12/2/2021, Accepted 26/5/2021, Published Online First 20/1/2022, Published 1/8/2022



This work is licensed under a [Creative Commons Attribution 4.0 International License](https://creativecommons.org/licenses/by/4.0/).

### Abstract:

Increase in unconventional resources of calcium ( $\text{Ca}^{+2}$ ) for fowls, aquaculture and native animals was improved. This work was planned to define the most polymorph of calcium carbonate ( $\text{CaCO}_3$ ) that take place in the two types of chicken eggshells (local and imported type). In this research, the comparative analysis of calcium carbonate ( $\text{CaCO}_3$ ) content was approved for nominated eggshells of native strain and imported chicken via Field Emission Scanning Electron Microscope (FESEM), Transmission Electron Microscope (TEM), Fourier-Transform Infrared Spectroscopy (FTIR) and Powder X-Ray Diffraction (PXRD) analysis. The results demonstrate that native and imported chicken eggshells comprise calcite morph that had shape between rhombohedral and spherical with distinguished pores distribution in the surface and crystallization size (31) nanometer for local chicken eggshells and (32) nanometer for import chicken eggshells respectively. The authors brief their results that local and import chicken eggshells had the top resources of calcium carbonate ( $\text{CaCO}_3$ ).

**Key words:** Chicken egg shells, EM, Nanopowder, Production, Physiochemical analysis, Reusing.

### Introduction:

Chicken eggshells are discarded resources from native bases for example hatcheries, homes and fast food productions<sup>1</sup> and are liable to be freely collected adequately. Eggshells discarded clearance ads to conservational contamination. Challenges related with discarding of eggshells consist of cost, accessibility of throwing away places, odour, flies and harshness<sup>2</sup>. Furthermore, chicken eggshells discarded treating is presently produced at huge quantities of numerous tons per day<sup>3</sup>. Furthermost eggshell remaining is thrown away since additional treating is too costly and burdensome<sup>4</sup>. Numerous researchers have been observed for methods to use the eggshells discarded, such as, via eggshells powder as a steadying material for cultivating soil properties, Ultraviolet-protecting essences<sup>5,6</sup> and as a basis of Calcium in human diet<sup>7</sup>.

$\text{Ca}^{+2}$  measures comprise carbonate, citrate, or gluconate salts that are not every time in effect<sup>8</sup>. For that reason, ordinary bases of minerals and vitamins are becoming further prevalent<sup>9</sup>. Eggshell

$\text{Ca}^{+2}$  is the superlative ordinary basis of calcium and it is around 90% absorbable than oyster shells, limestone or coral bases<sup>10,11</sup>. The structure of an eggshell is exactly like that of our bones and teeth<sup>10,12</sup>.

$\text{CaCO}_3$ , a pharmaceutical excipient, is principally recycled as diluent in solid dose formulae. It is furthermore recycled as a base for medicinal and dental preparations, buffering and dissolution assistance in dispersible tablets, in addition to food chemical addition and calcium complement<sup>13,14,15,16</sup>.

Currently, there is an excessive attention in the discovery of novel unpolluted  $\text{CaCO}_3$  sources.  $\text{CaCO}_3$ , gained from bones flour, does not comprise similar bioavailability of  $\text{Ca}^{+2}$  gotten from artificial bases.  $\text{CaCO}_3$  from eggshells has a benefit for not having toxically rudiments<sup>17</sup>.

Conferring to this information, a novel skill of eggshells treating was established. Egg productions harvest excessive quantity of shells and their concluding purpose is a conservational effect

challenge. This research is planned to organize and estimate  $\text{CaCO}_3$  from egg shell as it has a probable presentation in the development of a novel opportunity of pharmaceutical excipient, bone scaffold development, teeth manufacturing and drug carrier and delivery. The absence of data on these topics advises that there is a hopeful area to be discovered<sup>18</sup>, and these resources will permit quick progresses in relative studies of the organic elements of chicken eggshells and their practical consequences<sup>13</sup>.

The main objective of this study is to discover an ecologically and economically interesting usage of discarded chicken eggshells by rotating them into nanoparticles that can be recycled as steady material for refining soil properties, to progress of a novel choice of pharmaceutical excipient, bone scaffold development, teeth manufacturing and drug carrier and delivery. The particular objective of this study is to explore the physical-chemical of  $\text{CaCO}_3$  gotten from diverse bases of chicken egg shells.

### Materials and Methods:

The chicken eggs (*Gallus gallus*) of the different sources (local and import (Turkey origin)) (selected the white color one) were bought from Mosul markets, then weighted on a weighing balance (Sartorius AG Gottikåen, GP5202, d=0.01g, Germany), broken into a beaker. The raw eggshells were washed under tap water till the egg albumen was totally removed and peel off all of the shell's membranes from inside the shells. The shells were washed with deionized water then wrapped with a toilet paper to dry the water contented. Lastly the shells were weighed and ground into a fine powder using blender, weighted, then sieved through  $\leq 75 \mu\text{m}$  sieve. The sieved powder was additionally dehydrated in the lab oven at fifty Celsius degree for 120 hours and converted into nanoparticles using a mechanical method in the existence of Ball mill (Wisd® Ball Mill, Korea) for 7days then kept at fifty Celsius degree in a sterilized bottle previous to usage<sup>19, 20</sup>.

### Chicken eggshells description

#### Electron Microscopy (EM)

Analysis of prepared nanoparticles was done by FESEM tracked by image exploration with their particular software correspondingly and a transmission electron microscope (TEM) (Hitachi H-7100, Japan) for detecting the shape and size of the nanoparticles. For FESEM analysis, the samples were individually prepared, covered with gold and viewed<sup>21, 22</sup>. The chicken eggshells nano powder was liquefied in ninety nine percentage ethanol and

sonicated for thirty mins. (1-3) droplets of suspension was loaded on top of the carbon-enclosed copper grid and positioned on a filter paper to dehydrate at lab temperature previously observing by TEM<sup>23, 24</sup>.

### FTIR analysis

The biochemical tests were completed by FTIR in a variety of two hundred and eighty to four thousands  $\text{cm}^{-1}$  at a determination of two  $\text{cm}^{-1}$  and by a scan speediness of sixty four/s. The tablets of the nanoparticles chicken eggshells powders were examined separately in a mass percentage of one weight percentage in Kbr powder, and tests were achieved over Ultra Attenuated Total Reflection (UATR) methods<sup>25, 26</sup>.

### PXRD examination

One to two grams of powder of two form of eggshells were recycled for this examination. The examination required the performance of extensive-direction XRD to distinguish the nature and crystal-like apparatuses of the examples. All crystal-like stages existing were documented using XRD analyzer (Angstrom Advanced Inc. ADX-2700, X-Ray Powder diffraction Instrument) over the use of  $\text{CuK}\alpha$  ( $\lambda=1.540562 \text{ \AA}$ ) at forty kV and thirty mA<sup>27</sup>.<sup>28</sup>. The deflection formula was calm at a speed of perusing 0.02 degrees/s in  $2\theta$  at a variety of ( $5^\circ - 60^\circ$ ) at  $37^\circ\text{C}$ . XRD by Scherrer's formulation to match with the standards gotten from Transmission Electron Microscopy examination. The crystal-like sizes (Dv) is an informal procedure that flexibly differentiates among straining and dimension made peak lengthening overseeing the peak measurement as a meaning of Two theta<sup>29</sup>.

### Results:

The study involved recycling of chicken eggshells (local and import) and proportional examination of  $\text{CaCO}_3$  contented in them, which contain percentage method of analysis via using (7) chicken eggs of each type (Table 1 and 2).

**Table 1. Percentage analysis of micropowder of (7) local chicken eggshells.**

No. of sample	whole weight of local chicken egg (g)	whole weight of local chicken eggshell (g)	Percentage of whole weight of local chicken eggshell (g)/ whole weight of local chicken egg (g)	whole weight of local chicken eggshell micropowder (g) / whole weight (g)	Percentage of whole weight of local chicken eggshell micropowder (g) / whole weight of local chicken egg (g)
1	48.01	5.64	11.75	5.55	98.404
2	48.78	5.43	11.132	5.35	98.527
3	45.73	5.51	12.049	5.46	99.093
4	50.58	5.91	11.684	5.79	97.97
5	51.45	5.7	11.079	5.52	96.842
6	51.69	5.54	10.718	5.49	99.097
7	48.34	5.36	11.088	5.11	95.335
Average	49.23	5.58	11.36	5.47	97.90

**Table 2. Percentage analysis of micropowder of import (7) chicken eggshells.**

No. of sample	whole weight of import chicken egg (g)	whole weight of import chicken eggshell (g)	Percentage of whole weight of import chicken eggshell (g)/ whole weight of import chicken egg (g)	whole weight of import chicken eggshell micropowder (g) / whole weight (g)	Percentage of whole weight of import chicken eggshell micropowder (g) / whole weight of import chicken egg (g)
1	68.22	7.28	10.671	6.79	93.27
2	70.74	6.7	9.471	6.6	98.51
3	66.78	6.62	9.913	6.52	98.9
4	66.42	6.32	9.515	6.26	99.1
5	69.07	6.65	9.628	6.52	98.05
6	66.43	6.39	9.619	6.29	98.44
7	66.12	5.93	8.969	5.84	98.482
Average	67.68	6.56	9.68	6.40	97.82

Physical picture data (texture, color and hardness) of local and import chicken eggshells are existing in Table 3.


**Table 3. Physical description of local and import chicken eggshells.**

Type of eggshell	Physical characterization		
	Texture	Color	Hardness
Local chicken eggshells	Very smooth	off-white	Hard
Import chicken eggshells	Smooth	White	Semi-hard


### Description of chicken eggshells nanoparticles

The FESEM and TEM for nanoparticles shown calcite calcium carbonate nanoparticles with shape between rhombohedral and spherical with distinguished pores distribution in the surface but the spherical shape is dominates than the other shape and with a regular size of  $\leq 100$  nm for FESEM (Fig. 1) and with variety size of  $\leq 50$  nm

(Fig. 2) for TEM. There was no modification in the elemental structures of the gotten  $\text{CaCO}_3$  calcite nanoparticles powder after production using of roller mill method. This reveals the roll milling benefits in the breakdown of the larger sized calcite rods into smaller spherical ones with pores on their surfaces.

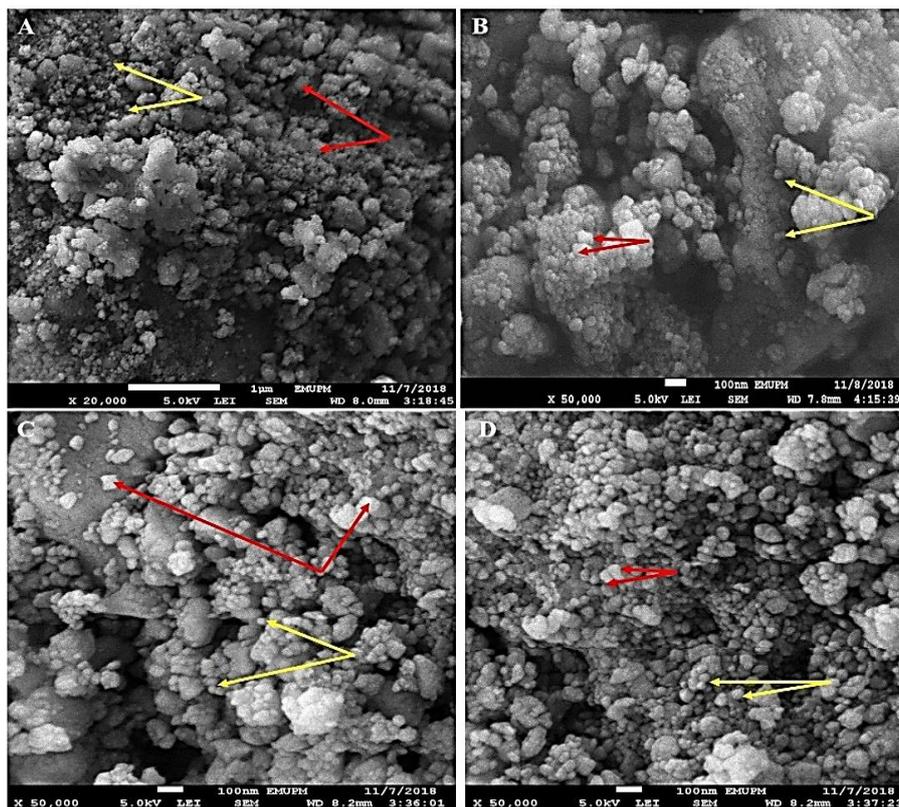

**Figure 1. FESEM micrographs of local (A&B) and import (C&D) chicken eggshells. The FESEM micrograph shows that both kinds of chicken eggshells have construction between rhombohedral (red arrows) and spherical (yellow arrows) shape of particle size, magnification of 50000 X.**

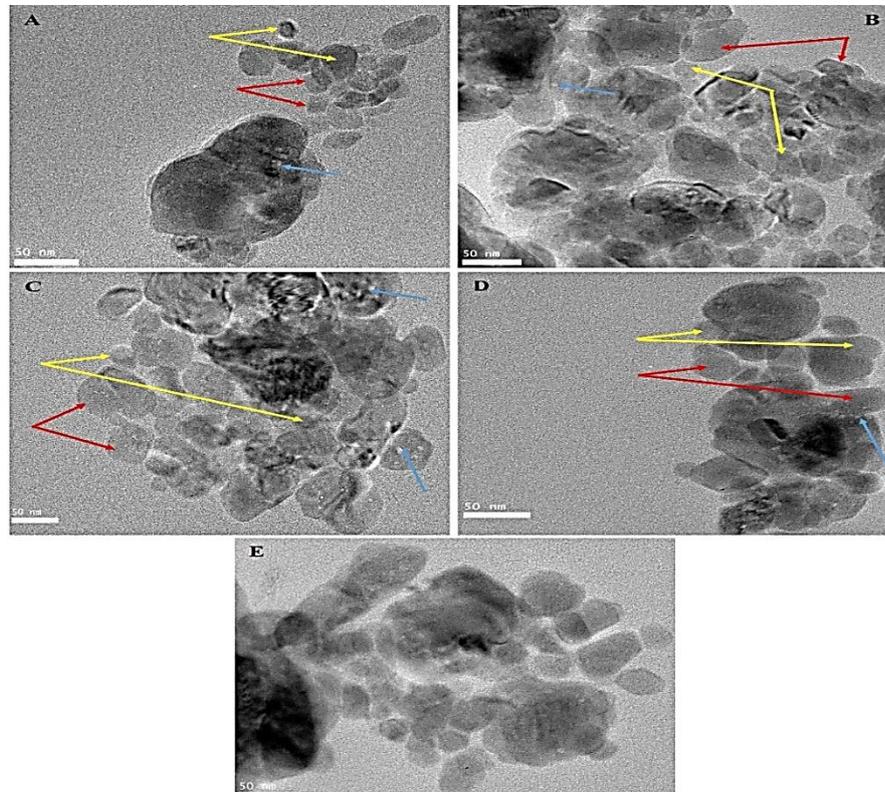

**Figure 2. TEM micrographs of local (A&B) and import (C, D &E) chicken eggshells. The TEM micrograph shows that both kinds of chicken eggshells have construction between rhombohedral (red arrows) and spherical (yellow arrows) shape crystal with hollows on their surfaces (blue arrows), magnification of 50 nm.**

### FTIR investigation

FTIR bands and variety of the main bands of the chicken eggshells nano powder are presented in (Fig. 3). In both kinds of chicken eggshells, different design of spectra was detected. The bands characterize some main sets demonstrating the stretching of hydroxyl, carbonyl and oxygen groups.

The existence of C-O, C=O, C=C and Ca-CO groups of the calcite bands of  $\text{CaCO}_3$  were also described. The absorbance spectrum of  $\text{CaCO}_3$  nano powder presented bands at  $1402.82\text{-}1405.59\text{ cm}^{-1}$ ,  $873.18\text{-}873.72\text{ cm}^{-1}$  and  $710.38\text{-}710.72\text{ cm}^{-1}$  for both kind of chicken eggshells due to carbonate ( $\text{CO}_3$ ).

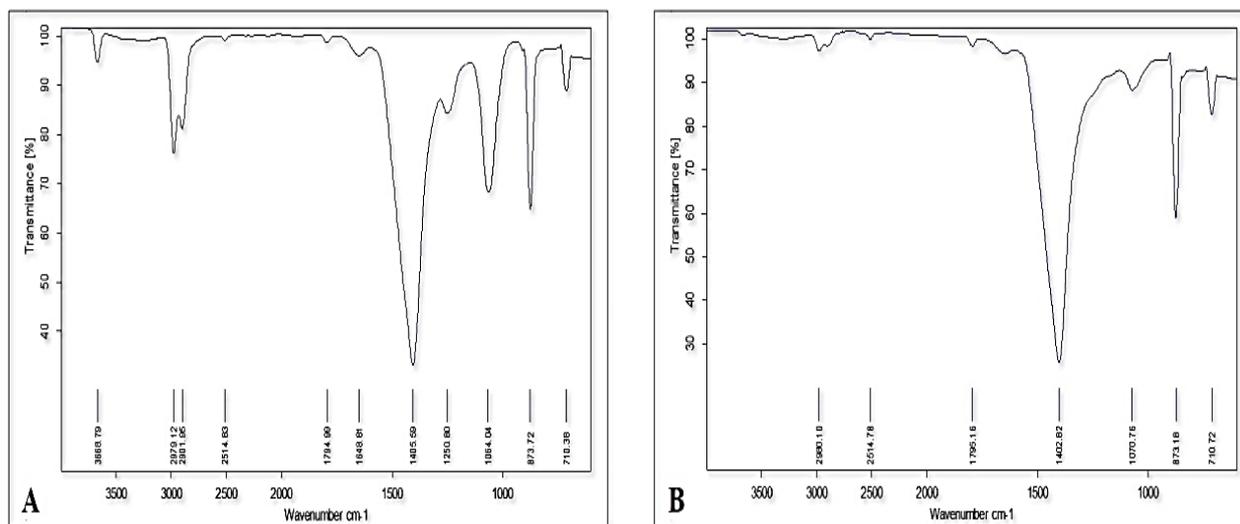


Figure 3. FTIR analysis of local (A) and import (B) chicken eggshells.

### PXRD investigation

PXRD outline of the ready chicken eggshells nano powder is presented in (Fig. 4). The XRD examination is a penetrating assessment intended for the acknowledgement of crystal-like phases of mineral combinations. Crystallinity phases were determined with diffraction angles from  $5\text{-}60^\circ$  at thirty seven Celsius degree. Fig. 4 indicates that PXRD captivation peaks in the nano powders harmonized each other. This indicate that the crystal-like value of calcite calcium carbonate nanoparticles in these concentrates is retained during the procedure of manufacture. Four noticeable peaks established each in  $\text{CaCO}_3$  calcite nanoparticles powder bands. The primary set of peaks were in two  $\theta = 23.08^\circ\text{-}29.357^\circ$ , while the additional set were in two  $\theta = 31.436^\circ\text{-}39.447^\circ$  and the other set were in two  $\theta = 43.195^\circ\text{-}48.55^\circ$  and last set were in two  $\theta = 56.555^\circ\text{-}58.141^\circ$

(Table 4 and 5). This indicate that the crystal-like value of  $\text{CaCO}_3$  calcite nanoparticles powder was preserved during the procedure of manufacture. These results are associated to a typical  $\text{CaCO}_3$  structure ICDD-card number 01-083-1762. The PXRD examination done presented vital data on crystal phase of the ingredients present in the eggshells. The obtained data from the bands recognized the presence of the characteristic peaks of calcite. PXRD and TEM approaches were castoff to examine the phase outline, the shape and dimension of prepared calcium carbonate concentrate. PXRD outlines of eggshells concentrates are similar and show several deflection topics that might be assigned to rhombohedral and spherical crystal-like construction with crystallite size 31 and 32 nm for local and import chicken eggshell, respectively.

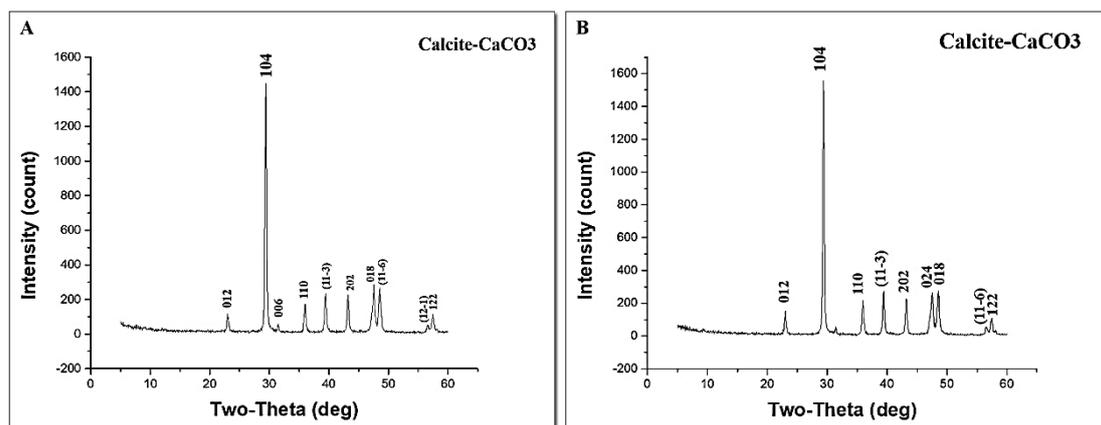


Figure 4. PXRD analysis of local (A) and import (B) chicken eggshells.

Table 4. PXRD analysis of nanopowder of (7) local chicken eggshells.

2-Theta	d(nm)	(h	k	l)	BG	Height	I%	Area	I%	FWHM	XS(nm)
23	0.38636	(0	1	2)	9	97	6.8	658	6.6	0.288	28
29.4	0.30355	(1	0	4)	12	1426	100	10019	100	0.299	27
31.449	0.28423	(0	0	6)	13	37	2.6	143	1.4	0.164	51
35.995	0.2493	(1	1	0)	10	160	11.2	1252	12.5	0.333	25
39.447	0.22824	(1	1	3)	13	218	15.3	1654	16.5	0.322	26
43.203	0.20923	(2	0	2)	9	213	14.9	1591	15.9	0.317	27
47.549	0.19107	(0	1	8)	13	264	18.5	2584	25.8	0.416	20
48.55	0.18736	(1	1	6)	11	250	17.5	2322	23.2	0.395	22
56.555	0.16259	(1	2	1)	6	42	2.9	304	3	0.308	29
57.456	0.16026	(1	2	2)	13	97	6.8	819	8.2	0.359	25

2 theta: the diffracted angle, h,k,l: Miller indices of plane, BG: Back Ground, I: Intensity, Area: Area under the peak, FWHM: Full Width of Half Maximum, XS (nm): crystal size (nm).

Table 5. PXRD analysis of nanopowder of (7) import chicken eggshells.

2-Theta	d(nm)	(h	k	l)	BG	Height	I%	Area	I%	FWHM	XS(nm)
23.038	0.38574	(0	1	2)	8	141	8.9	692	9.2	0.283	28
29.357	0.30398	(1	0	4)	24	1533	100	10274	100	0.284	29
31.436	0.28434	(0	0	6)	15	39	2.2	147	2.5	0.223	37
35.946	0.24963	(1	1	0)	12	206	14.7	1077	13.4	0.283	29
39.399	0.22851	(1	1	3)	244	259	20.2	1897	16.9	0.33	25
43.195	0.20927	(2	0	2)	10	213	16.1	1492	13.9	0.29	29
47.501	0.19125	(0	1	8)	13	240	21.7	2640	15.7	0.423	20
48.543	0.18739	(1	1	6)	11	259	23.2	2304	16.9	0.4	21
56.598	0.16248	(1	2	1)	4	44	4.2	318	2.9	0.375	24
57.489	0.16017	(1	2	2)	8	91	11.8	873	5.9	0.422	21
58.141	0.15853	(1	0	0)	6	24	1.2	151	1.6	0.279	32

2 theta: the diffracted angle, h,k,l: Miller indices of plane, BG: Back Ground, I: Intensity, Area: Area under the peak, FWHM: Full Width of Half Maximum, XS (nm): crystal size (nm).

## Discussion:

Conferring to (30) shell is about 11.36% of the total weight of the local egg (local egg weight ~ 49 gram) and 9.69% of the total weight of the import egg (import egg weight ~ 68 gram) and it presents substances of calcium carbonate. So, egg shell is a rich basis of mineral salts, chiefly calcium carbonate type calcite form .

The eggshells contain chiefly  $\text{CaCO}_3$ , therefore calcium shows an essential part in the eggshells construction through FTIR and PXRD analysis. The previous studies showed that the chief structure material of the shell is  $\text{CaCO}_3$  (96%), and the residual modules are magnesium, phosphorus, but also copper, zinc, iron and numerous trace

elements, amongst them lithium, strontium and bar. They described that wholly egg shells obligated parallel biochemical substances that mostly consist of calcium carbonate and other additional elements; for example S, Mg, P, Al, K and Sr<sup>31, 32, 33, 34</sup>.

These results confirm the studies by Solomon<sup>35</sup> and Dennis et al.<sup>36</sup> demonstrating calcite as the crystal construction of the Leghorn hen eggshells. A comparable outcome was described from the analysis of the biochemical structure of normal and boiled hen egg shells by XRD<sup>37</sup>.

The eggshells ultrastructure was detected using SEM presented in (Fig. 1), obtained from raw local and import eggs. Under low and high

magnification (20000-50000X), there was not much change in SEM micrograph between local and import chicken eggshells.

Both types of chicken eggshells express a particle size of  $\leq 50$  nm ( $\text{CaCO}_3$ -calcite form). The reduction of the crystal size can be recognized to the roll mill process. Also, the higher strength peaks for local and import chicken eggshells in FTIR and PXRD results could be associated with the decrease in the crystallite size. The XRD design peaks accorded the peaks of calcite  $\text{CaCO}_3$  ICDD No. 85-11108 marvelously and agree with the results of Kamkum et al.<sup>3</sup> and Murakami et al.<sup>18</sup>.

SEM and TEM description is used to conclude the morphology of any kind of nanoparticles<sup>38, 39, 40</sup>, especially here for  $\text{CaCO}_3$  nano powders. The SEM images of the  $\text{CaCO}_3$  from both types of chicken eggshells are presented in (Fig. 1 and 2). These images indicate that the  $\text{CaCO}_3$  powders are between rhombohedral and spherical shape with distinguished pores distribution in the surface with a typical size of  $\sim 50$  nm. The eggshell powder designates the existence of agglomeration. This is so because of the existence of other phosphate compounds in the formula of tricalcium phosphate (TCP). This remark agrees with the results described by Kalita and Verma<sup>41</sup> and Syafaat<sup>42</sup>.

The chicken eggs are spent often in plenty amounts, but till now the shells are unused and static infrequently used particularly as a source of calcium or  $\text{CaCO}_3$  material that can be good micro or nano-materials for the removal of toxic heavy metals as a noble substantial in the management of strong acidic waste water as well as a good neutralization capacity, development of a novel opportunity of pharmaceutical excipient, bone scaffold development, teeth manufacturing and filling; and drug carrier and delivery for bone disorders and diseases.

### Conclusion:

Chicken eggshells from the hatcheries, fast food productions and homes must not be predisposed in a method that contaminates the environment. The properties of local and import chicken eggshells are recognized with SEM, TEM, XRD and FTIR analyses. After analysis, the greatest structure of eggshell is ( $\text{CaCO}_3$ ) in addition to the distributions of pores on the surface of nanoparticles detected. From the results of this study, we recommend using chicken eggshell nano powder as a worthy substantial in the handling of tough acidic waste water over a reasonable application of heavy metal ions in addition a worthy deactivation capability, development of a novel opportunity of

pharmaceutical excipient, bone scaffold development, teeth manufacturing and filling; and drug carrier and delivery for bone disorders and diseases.

### Acknowledgment:

The authors thank the Department of Anatomy in College of Veterinary Medicine, University of Mosul, for supporting this study.

### Authors' declaration:

- Conflicts of Interest: None.
- We hereby confirm that all the Figures and Tables in the manuscript are mine ours. Besides, the Figures and images, which are not mine ours, have been given the permission for re-publication attached with the manuscript.
- The author has signed an animal welfare statement.
- Ethical Clearance: The project was approved by the local ethical committee in University of Mosul.

### Authors' contributions:

S.M., G.S., S.E. and A.A. contributed to the design and implementation of the research, to the analysis of the results and to the writing of the manuscript.

### References:

1. Owuamanam S, Cree D. Progress of bio-calcium carbonate waste eggshell and seashell fillers in polymer composites: a review. *J. Compos. Sci.* 2020; 4 (70): 1-22.
2. Ajala EO, Eletta OAA, Ajala MA, et al. Characterization and evaluation of chicken eggshell for use as a bio-resource. *Arid Zone J Eng. Tech. Enviro.* 2018; 14 (1): 26-4.
3. Kamkum P, Atiwongsangthong N, Muanghlua R, et al. Application of chicken eggshell waste as a starting material for synthesizing calcium niobate ( $\text{Ca}_4\text{Nb}_2\text{O}_9$ ) powder. *Ceram. Int.* 2015; 41 (Suppl. S1): S69-S75.
4. Awogbemi O, Inambao F, Onuh EI. Modification and characterization of chicken eggshell for possible catalytic applications. *Heliyon* 2020; 6: e05283.
5. Fecheyr-Lippens D, Nallapaneni A, Shawkey MD. Exploring the use of unprocessed waste chicken eggshells for uv-protective applications. *Sustainability.* 2017; 9: 232.
6. Fecheyr-Lippens DC, Igic B, D'Alba L, et al. The cuticle modulates ultraviolet reflectance of avian eggshells. *Biol. Open* 2015; 4:753-9.
7. Bartter J, Diffey H, Yeung YH, et al. Use of chicken eggshell to improve dietary calcium intake in rural sub-Saharan Africa. *Matern. Child Nutr.* 2018; 14 (S3): e12649.

8. Ueda Y, Taira Z. Effect of anions or food on absolute bioavailability of calcium from calcium salts in mice by pharmacokinetics. *J Exper Pharma*. 2013; 5: 67–1.
9. Oliveira A, Benelli P, Amante ER. A literature review on adding value to solid residues: egg shells. *J Cleaner Prod*. 2013; 46: 42–7.
10. Kingori AM. A Review of the uses of poultry eggshell and shell membranes. *Int J Poult Sci*. 2011; 10 (11): 908-2.
11. Szeleszczuk L, Pisklak DM, Kuras M, et al. *In vitro* dissolution of calcium carbonate from the chicken eggshell: on the study of calcium bioavailability. *Int J Food Proper*. 2015; 18: 2791–9.
12. Neunzehn J, Szuwart T, Wiesmann HP. Eggshells as natural calcium carbonate source in combination with hyaluronan as beneficial additives for bone graft materials, an *in vitro* study. *Head & Face Med*. 2015; 11:12.
13. Hincke MT, Nys Y, Gautron J, et al. The eggshell: structure, composition and mineralization. *Frontiers Bioscie*. 2012; 17:1266-80.
14. Guarderas F, Leavell Y, Sengupta T, et al. Assessment of chicken-egg membrane as a dressing for wound healing. *Adv Skin Wound Care*. 2016; 29 (3):131-40.
15. Ahmed TA, Suso HP, Hincke MT. In-depth comparative analysis of the chicken eggshell membrane proteome. *J proteomics*. 2017; 155: 49-62.
16. Vuong TT, Rønning SB, Ahmed TAE, et al. Processed eggshell membrane powder regulates cellular functions and increase MMP-activity important in early wound healing processes. *PLOS ONE*. 2018.
17. Macneil J. Composition of egg shell. *Egg industry*. 1997; 102: 15-7.
18. Murakami FS, Rodrigues PO, De Campos CMT, et al. Physicochemical study of CaCO<sub>3</sub> from egg shells. *Ciênc Tecnol Aliment Campinas*. 2007; 27 (3): 658-2.
19. Mahmood SK, Zakaria MZAB, Razak ISA, et al. Preparation and characterization of cockle shell aragonite nanocomposite porous 3D scaffolds for bone repair. *Biochem Biophys Reports* 2017; 10: 237–51.
20. Mahmood SK, Razak ISA, Ghaji MS, et al. *In vivo* evaluation of the novel nanocomposite porous 3D scaffold in a rabbit model: histological analysis. *Int J Nanomed*. 2017; 12: 8587—98.
21. Isa T, Zakaria ZAB, Rukayadi Y, et al. Antibacterial activity of ciprofloxacin-encapsulated cockle shells calcium carbonate (aragonite) nanoparticles and its biocompatibility in macrophage J774A. *Int J Mol Sci*. 2016; 17 (5):713.
22. Mahmood SK, Zakaria ZAB, Razak ISA, et al. *In Vivo* evaluation of the novel nanocomposite porous 3d scaffold in a rabbit model: hematology and biochemistry analysis. *Iraqi J Vet Sci*. 2019; 32 (2):219-30.
23. Islam KN, Bakar MZBA, Ali ME, et al. A novel method for the synthesis of calcium carbonate (aragonite) nanoparticles from cockle shells. *Powder Technol*. 2013; 235: 70–5.
24. Ibrahim SM, Mahmood SK, Razak ISA, et al. Characterization and *in vitro* evaluation of a novel coated nanocomposite porous 3d scaffold for bone repair. *Iraqi J Vet Sci*. 2019; 33 (1): 157-73.
25. Hammadi NI, Abba Y, Hezmee MNM, et al. Formulation of a sustained release Docetaxel loaded cockle shell-derived calcium carbonate nanoparticles against breast cancer. *Pharma Res*. 2017; 34 (6): 1193–03.
26. Mahmood SK, Razak ISA, Ibrahim SM, et al. *In Vivo* evaluation of the novel nanocomposite porous 3d scaffold in a rabbit model. *Indian J Sci Tech*. 2018; 11(19):1-15.
27. Venkateswarlu K, Sreekanth D, Sandhyarani M, et al. X-ray peak profile analysis of nanostructured hydroxyapatite and fluorapatite. *Int J Biosci Biochem Bioinform*. 2012; 2 (6): 389-3.
28. Mahmood SK, Razak ISA, Yusof LM, et al. *In vitro* evaluation of the cockle shells aragonite nanocomposite porous 3d scaffolds for bone repair. 6<sup>th</sup> Int Conf Nanotech, Adv Mater Applica. Nanotechnology and Advanced Materials Research Center, University of Technology, Baghdad, Iraq. Available online at <http://namrc.uotechnology.edu.iq/index.php/> Nanotechnology and Advanced Materials Research Centre, Proceeding Articles Book 4, 2018, special issue: 1020-44.
29. Jaji AZ, Zakaria ZAB, Mahmud R, et al. Safety assessments of subcutaneous doses of aragonite calcium carbonate nanocrystals in rats. *J Nanopart Res*. 2017; 19:175.
30. Kunanuruksapong TR, Sirivat A. Preparation and properties of calcium oxide from eggshells via calcination. *Mater Sci-Poland*, 2012; 30 (4): 313-22.
31. Fajrah MC. Identification of calcium carbonate (CaCO<sub>3</sub>) characteristics from different kinds of poultry eggshells using x-ray diffraction (XRD) and Fourier transformation infra-red (FTIR). 7th Int Conf Phys Applica. 2014 (ICOPIA 2014): 138-2.
32. Dolińska B, Jelińska M, Szulc-Musio B, et al. Use of Eggshells as a Raw Material for Production of Calcium Preparations. *Czech J. Food Sci.*, 2016; 34 (4): 313–7.
33. Shwetha A, Dhananjaya, Kumara SM, et al. Comparative study on calcium content in egg shells of different birds. *Int J Zoo Stu*. 2018; 3 (4): 31-33.
34. Dizaj SM, Sharifi S, Ahmadian E, et al. An update on calcium carbonate nanoparticles as cancer drug/gene delivery system. *Expert Opinion Drug Deliv*. 2019: 1587408.
35. Solomon S E. Egg and eggshell quality. Wolfe Publishing Ltd., London, England. 1991.
36. Dennis JE, Xiao SQ, Agarwal M. Microstructure of matrix and mineral components of eggshells from white Leghorn chickens (*Gallus gallus*). *J Morpho*. 1996; 228: 287-06.
37. Arunlertaree C, Kaewsomboon W, Kumsopa A et al. Removal of lead from battery manufacturing waste water by egg shell. *Songklanakarin J Sci Technol*. 2007; 29: 857–68.

38. Dleam E A, Kareem S H. Mesoporous silica nanoparticles as a system for ciprofloxacin drug delivery; kinetic of adsorption and releasing. Baghdad Sci J. 2021; 18 (2): 0357.
39. Abdulghani A J, Al-Ogedy W M. Synthesis and characterization of multishapes of  $Fe_3O_4$  nanoparticle by solve-hydrothermal method using microwave radiation. Baghdad Sci J. 2016; 13 (2): 0331.
40. Ayal A K. Enhanced photocurrent of Titania nanotube photoelectrode decorated with CdS nanoparticles. Baghdad Sci J. 2018; 15 (1): 0057.
41. Kalita J, Verma S. Nanocrystalline hydroxyapatite bioceramic using microwave radiation: Synthesis and characterization. Mater Sci Eng. C 2010; 30: 295
42. Syafaat FY, Master Thesis, Universitas Gadjah Mada, 2017. Gary D. Butcher, D.V.M., Ph.D., professor; and Richard Miles, Ph.D., professor, College of Veterinary Medicine, UF/IFAS Extension, Gainesville FL 32611.

## إعادة تدوير قشر بيض الدجاج إلى مسحوق نانوي: التركيب والخصائص

عمار غانم محمد الحايك<sup>1</sup>

شهباء خليل ابراهيم<sup>2</sup>

غادة عبد الرحمن سلطان<sup>1</sup>

سفانة خضر محمود<sup>1</sup>

<sup>1</sup> فرع التشريح، كلية الطب البيطري، جامعة الموصل، الموصل، العراق.  
<sup>2</sup> فرع الامراض، كلية الطب البيطري، جامعة الموصل، الموصل، العراق.

### الخلاصة:

تم تحسين الموارد غير التقليدية من الكالسيوم ( $Ca^{+2}$ ) للطيور والأحياء المائية والحيوانات المحلية. تم التخطيط لهذا البحث لتحديد أكثر أنواع كربونات الكالسيوم تعددًا ( $CaCO_3$ ) التي تحدث في نوعي قشر بيض الدجاج (النوع المحلي والنوع المستورد). في هذا البحث، تمت العمل على التحليل المقارن لمحتوى كربونات الكالسيوم ( $CaCO_3$ ) لقشر البيض من السلالة المحلية والمستوردة عبر اجراء تحليل المجهر الإلكتروني لمسح الانبعاث الميداني (FESEM)، ومجهر الإرسال الإلكتروني (TEM)، والتحليل الطيفي للأشعة تحت الحمراء (FTIR) و تحليل حيود الشعاع للمسحوق (PXRD). أظهرت النتائج أن قشر بيض الدجاج الأصلي والمستورد يشتمل على شكل الكالسييت الذي له شكل بين المعيني والكروي مع توزيع مسام مميز في السطح وحجم تبلور (31) نانومتر لقشر بيض الدجاج المحلي و (32) نانومتر لقشر بيض الدجاج المستورد على التوالي. يوجز الباحثون نتائجهم بأن قشر بيض الدجاج المحلي والمستورد يحتوي على أعلى موارد كربونات الكالسيوم ( $CaCO_3$ ).

**الكلمات المفتاحية:** إعادة الاستخدام، الإنتاج، مسحوق النانو، المجهر الاليكتروني، التحليل الفيزيوكيميائي، قشر بيض الدجاج.